

Triethylamine and TBD supported on silica: useful heterogeneous catalysts for the reaction of β -dicarbonyl derivatives with α,β -unsaturated compounds under batch and continuous flow conditions

Raimondo Maggi,* Calogero G. Piscopo, and Giovanni Maestri

*“Clean Synthetic Methodology Group”, Dipartimento di Chimica dell’Università
Parco Area delle Scienze 17A, I-43124 Parma, Italy
E-mail: raimondo.maggi@unipr.it*

Dedicated to Professor Manfred Schlosser in honor of his scientific achievements

DOI: <http://dx.doi.org/10.3998/ark.5550190.p009.025>

Abstract

The synthesis of either mono- or *bis*-adducts via Michael reaction between active methylene compounds and α,β -unsaturated reagents is reported. These processes are catalyzed by two heterogeneous basic catalysts, namely KG-NEt₂ and KG-TBD. Both catalysts show good catalytic efficiency and can be reused several times fully preserving their efficiency. The process could be efficiently performed under continuous flow conditions obtaining promising results in term of yield and selectivity.

Keywords: Heterogeneous catalysis, basic catalysts, Michael reaction, continuous flow procedure

Introduction

The search for new, efficient and low-cost catalysts for organic transformation represents a basic area of research.¹⁻³ In this context heterogeneous catalysts are gaining importance as they represent a smart tool to carry out environmentally acceptable organic processes. While solid catalysts are mainly exploited in petrochemical and bulk chemistry transformations,⁴⁻⁵ there has been a great effort in the last decades to accomplish the synthesis of fine chemicals by means of heterogeneous catalysis.

As part of our ongoing interest in the preparation, characterization and use of catalysts supported on solid materials,⁶⁻⁹ we have synthesized two silica-supported organic bases, namely

triethylamine and 1,5,7-triazabicyclo[4.4.0]dec-5-ene (TBD), to study their behavior in heterogeneous catalyzed reactions. These bases are routinely used as homogeneous catalysts to promote Michael reactions between active methylene compounds and α,β -unsaturated reagents. This reaction represents indeed one of the most efficient methods for C-C bond formation and its wide application in organic synthesis is well documented.¹⁰ These reactions are usually performed in the presence of strong bases (*i.e.* alkali metal alkoxides and hydroxides),¹¹ transition metal complexes,¹² solid acids (*i.e.* alumina and clays),¹³⁻¹⁵ and Lewis acids (*i.e.* SnCl₄, TiCl₄ and ZrCl₄).¹⁶⁻¹⁸ More recently, TBD,¹⁹ silica-supported organic bases,²⁰ enzymes²¹ and microsized cerium chloride²² have been used to efficiently catalyze these reactions.

Results and Discussion

We report herein the preparation of two different organic bases anchored on silica gel (KG-NEt₂ and KG-TBD – Figure 1) pivoting on literature procedures²³⁻²⁴ and their use as catalysts in the reaction between an α,β -unsaturated compound and an active methylene reagent. Remarkably, it is possible to steer the selectivity towards either mono-alkylated products **3** or *bis*-alkylated adducts **4** depending on the strength of the basic catalyst (Scheme 1).


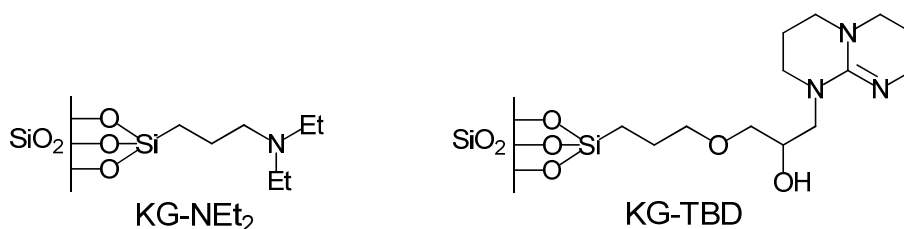


Figure 1. KG-NEt₂ and KG-TBD structures.

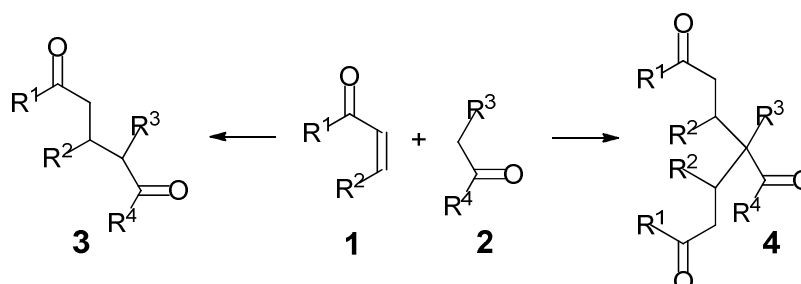

Scheme 1. *Mono*- and *bis*-adducts obtained by reacting active methylene compounds and α,β -unsaturated reagents.

These reactions were also performed in a continuous flow reactor. This strategy offers significant improvements compared to conventional batch processes due to a precise control of

residence time, heat and mass transport, and is thus a route to minimize wastes and develop more efficient and sustainable syntheses.²⁵

In a preliminary batch experiment, the model reaction of butenone (**1a** -10 mmol) and pentane-2,4-dione (**2a** -10 mmol) in toluene (10 mL) with 0.9 g of KG-NEt₂ (10% mol - loading: 1.1 mmol/g) has been carried out at room temperature. Upon 5 hours, the mono-alkylated Michael product **3aa** was isolated in a poor yield (9%) with high selectivity (100%). In order to boost conversion of substrate seeking to maintain similarly high selectivity, reactions were carried out at higher temperatures. Results are summarized in Table 1.

Table 1. Influence of the temperature on both yield and selectivity in the reaction of butenone with pentane-2,4-dione (1/1 molar ratio)

Entry	T (°C)	2a conversion (%)	3aa yield (%)	3aa selectivity (%)
a	25	9	9	100
b	50	56	51	91
c	75	79	63	80
d	100	97	70	72

By carrying out the reaction at 50 °C a remarkable increase of the yield was observed (51%, entry b) together with a good level of selectivity (91%). On the contrary, reactions carried out at higher temperatures showed slightly better yields with concomitant loss of selectivity (entries c and d).

We next investigated the amount of catalyst (Table 2).

Table 2. Influence of the catalyst amount on both yield and selectivity in the reaction of butenone and pentane-2,4-dione (1/1 molar ratio)

Entry	Catalyst (mol %)	2a conversion (%)	3aa yield (%)	3aa selectivity (%)
a	10	56	51	91
b	5	55	50	91
c	2.5	32	30	94

Gratifyingly, the same yield value together with an high level of selectivity was observed by halving the catalyst amount (51% and 91% respectively, entry a); reducing further the amount of KG-NEt₂ to 2.5 mol% preserved the high selectivity but proved to be detrimental for the yield (30%, entry c).

The influence of the solvent was then considered by testing acetonitrile, isopropanol and water in the model reaction. The reaction carried out in acetonitrile showed very low conversion (15%), whereas the same yield value observed with toluene was found with the other two more polar solvents (52 and 50% using isopropanol and water respectively). In these two cases however selectivity dropped to lower levels (84 and 70% respectively).

With best conditions in our hands (catalyst: 5% mol, 5 hours, 50 °C, toluene), we have then investigated the recycling of the heterogeneous catalyst (Table 3).

Table 3. Catalyst recycle

Entry	Run	2a conversion (%)	3aa yield (%)	3aa selectivity (%)
a	1	55	50	91
b	2	54	48	89
c	3	53	47	89
d	4	54	49	91
e	5	54	48	89

At the end of each reaction, the KG-NEt₂ catalyst has been recovered by filtration and reused for the next run upon a simple toluene washing (10 mL). We were pleased that the catalyst efficiency in terms of yield and selectivity remains fully preserved for the first five cycles. We then unambiguously confirmed that the catalyst is a heterogeneous species by applying the well known “hot filtration test”.²⁶

The second aim of the project has been to identify a suitable combination of catalyst and reaction conditions to selectively obtain *bis*-alkylated products **4**. Even by increasing the reaction time, the reaction temperature and the butanone/pentane-2,4-dione ratio it was not possible however to achieve good yield and selectivity of the target compound with the KG-NEt₂ catalyst. We ascribed this lack of reactivity to the low basicity of the catalyst; consequently we decided to prepare an heterogeneous catalyst, as KG-TBD, bearing a stronger base to perform this process. An encouraging result was achieved by carrying out the reaction in toluene for 5 hours at room temperature with 5 mol% of the catalyst with the tethered guanidine moiety (loading: 0.6 mmol/g) and with a 3/1 molar ratio of butenone/pentane-2,4-dione. We were then delighted to recover *bis*-adduct **4aa** in 91% yield and to observe almost complete selectivity towards this product (97%). On the contrary, by carrying out the reaction with a lower reagent ratio, a decrease in both yield and selectivity were observed.

We have then evaluated the influence of the catalyst amount on the efficiency of the process and results are reported in Table 4.

Table 4. Influence of the catalyst amount on both yield and selectivity in the reaction between butenone pentan-2,4-dione (3/1 molar ratio)

Entry	Catalyst (mol %)	2a conversion (%)	4aa yield (%)	4aa selectivity (%)
a	10	100	84	84
b	5	94	91	97
c	2.5	86	85	99

From the data reported we can conclude that by halving the catalyst amount (2.5 mol%, entry c) a lower yield was observed but the same very high selectivity was preserved; on the contrary, by doubling the KG-TBD amount, full conversion of pentane-2,4-dione was registered but both yield and selectivity were reduced (84% each, entry a). This behavior could be ascribed to the formation of cyclized products (not identified) due to intramolecular aldol condensation (Figure 2).

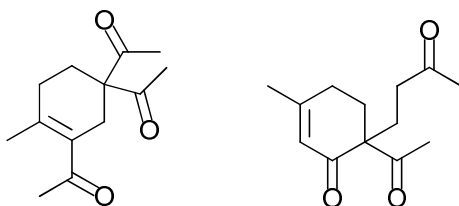


Figure 2. Possible by-products derived from intramolecular aldol condensation of **4aa** adduct.

With the two complementary methodologies to obtain either mono- or *bis*-adduct products using the same reagents by simply switching the heterogeneous catalysts and the molar ratio of substrates, we have then conceived to perform the reaction under continuous flow conditions.

For continuous flow experiments a simple process was set up using two empty HPLC columns (6.0 cm length x 0.8 cm inner diameter) packed with the two catalysts. Two pulsation-free syringe pumps were connected to the reactor allowing a precise control of the flow rate of the solution of each reagent; the two columns were placed in a GC oven in order to carefully control heating (Figure 3).

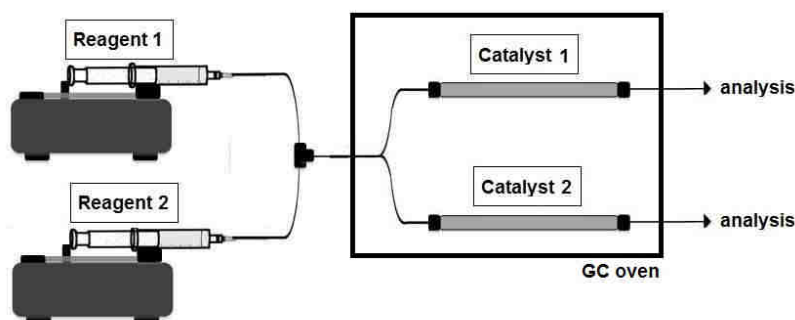


Figure 3. Schematic diagram of the reactor setup for the continuous flow process.


By carrying out the model reaction between butenone and pentan-2,4-dione (1:1 molar ratio) with KG-NEt₂ catalyst in toluene at 50 °C with a residence time of 15 minutes, product **3aa** was obtained in 20% yield with a selectivity value of 93%. Pivoting on this result, the reaction was further investigated through a systematic variation of key parameters such as temperature and residence time. The best result was achieved by performing the reaction at 50 °C and increasing

the residence time to 50 minutes tuning flow rates; the yield raised to 55% and a good level of selectivity was preserved (92%).

The best conditions to synthesize *bis*-alkylated product **4aa** were found flowing at room temperature butenone and pentane-2,4-dione in a 3:1 molar ratio through the column fitted with KG-TBD catalyst with a residence time of 40 minutes. Using this continuous flow process **4aa** was formed with 93% yield and 98% selectivity.

Finally we investigated the scope of the reaction under continuous flow conditions (Table 5).

Table 5. Preparation of various *mono*- and *bis*-adducts derived from the reaction between active methylene compounds and α,β -unsaturated reagents

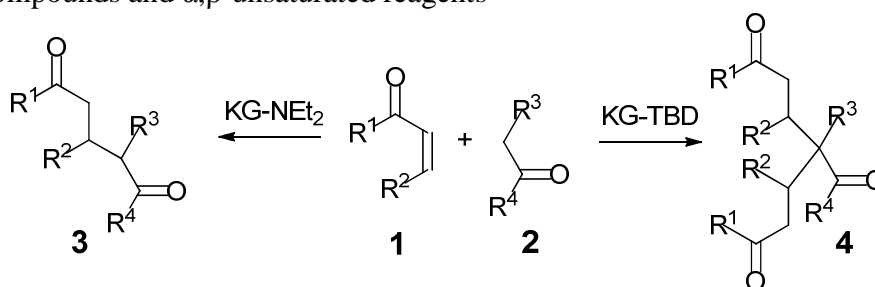

Reagents	Catalyst	R ¹	R ²	R ³	R ⁴	3 yield [sel] (%)	4 yield [sel] (%)
1a2a	KG-NEt ₂	Me	H	COMe	Me	55 [92]	-
1a2b	KG-NEt ₂	Me	H	COMe	OEt	50 [95]	-
1a2c	KG-NEt ₂	Me	H	NO ₂	OEt	87 [92]	-
1b2a	KG-NEt ₂	-(CH ₂) ₃ -		COMe	Me	71 [97]	-
1a2a	KG-TBD	Me	H	COMe	Me	-	93 [99]
1a2b	KG-TBD	Me	H	COMe	OEt	-	91 [98]
1a2c	KG-TBD	Me	H	NO ₂	OEt	-	96 [99]
1b2a	KG-TBD	-(CH ₂) ₃ -		COMe	Me	88 [97]	-

The results of Table 5 show that the *mono*-addition of active methylene compounds and α,β -unsaturated reagents can be accomplished with good yields (50-87%) and selectivities (92-97%) using KG-NEt₂ catalyst; by varying the reaction temperature and the relative flux of reagents it is possible to synthesize *bis*-adduct products **4** simply switching the desired catalyst column with very high yields (91-96%) and excellent selectivities. It is worth noting that 2-cyclohexenone delivers selectively *mono*-adduct product **3** only using both catalysts; the second addition of a 2-cyclohexenone molecule on the *mono*-addition product do not occur probably owing to the increased steric hindrance.

Conclusions

We reported that KG-NEt₂ and KG-TBD heterogeneous materials can be employed as catalysts with tunable basic strength to synthesize either *mono*- or *bis*-adduct products *via* Michael reaction of active methylene compounds and α,β -unsaturated reagents by slightly modifying reaction conditions. Remarkably, both processes can be carried out under continuous flow conditions simply by switching the feeding of reagents to the column with the desired catalyst. Through this approach it is possible to alternatively synthesize either *mono*- or *bis*-adduct products with very high yields and excellent selectivities by varying residence time and molar ratio of reagents.

Experimental Section

General. All the reagents and solvents were purchased from Aldrich and used without further purification. Amorphous silica used to prepare catalysts was purchased from Merck (Kieselgel 60, KG-60); prior to functionalization, the siliceous supports were dried at 300 °C for 15 hours. Elemental analyses to determine catalyst loading were performed using a Carlo Erba CHNS-0 EA1108 Elemental Analyzer. Gas-chromatographic analyses were accomplished on a TraceGC ThermoFinnigan instrument (FID).

KG-NEt₂. *N,N*-diethyl-3-aminopropyltrimethoxysilane (12.7 mmol, 3.0 g, 3.2 mL) was added to a suspension of previously dried KG-60 silica (3 g) in refluxing toluene (50 mL) and the mixture was kept under stirring for 1.5 h at the same temperature. Toluene and formed methanol were removed and the resulting solid was then poured again into refluxing toluene (50 mL) for 1.5 hours. This sequence was repeated two times. The modified solid was filtered, washed in a Soxhlet apparatus with diethyl ether (20 mL) and dichloromethane (20 mL) and eventually dried at 110 °C.

KG-TBD. TBD (87.2 mmol, 1 g) was added to a solution of 3-trimethoxysilylpropoxymethyloxirane (5.9 mmol, 1.3 mL) in dry DMF (10 mL) and the mixture was kept under stirring for 15 h at rt. The solution was then poured into a flask containing dry toluene (50 mL) and previously dried KG-60 silica (3.5 g). The resulting slurry was refluxed for 1 h and then methanol and toluene were distilled out. This operation was repeated 3 times. The resulting solid was then filtered, washed with toluene (20 mL), methylene chloride (20 mL) and methanol (20 mL) and eventually treated for 24 h in a Soxhlet apparatus using a 1/1 diethyl ether/methylene chloride mixture to afford the desired heterogeneous catalyst upon 2 h of vacuum drying.

Catalytic reactions under batch conditions. In a stirred batch reactor equipped with a condenser and a thermometer, toluene (10 mL), the selected active methylene compound (10 mmol), the desired α,β -unsaturated reagent (10 mmol to synthesize compounds **3** or 30 mmol for

the synthesis of products **4**) and the heterogeneous catalyst (0.9 g of KG-NEt₂ for the synthesis of **3** or 0.8 g of KG-TBD for products **4**) were stirred at either 50 °C (for compounds **3**) or at rt (for the synthesis of products **4**) for 5 hours. Then the solid catalyst was recovered by filtration and the reaction mixture was analyzed by high resolution capillary GC with a fused silica capillary column SPB-20 from Supelco (30 m x 0.25 mm) using decane as internal standard. The products were identified by comparing their spectral data with those reported in the literature.^{22,27-31}

Catalytic reactions under continuous flow conditions. A steel HPLC column (6.0 cm length x 0.8 cm inner diameter) was packed with 1.5 g of the selected catalyst (KG-NEt₂ for the synthesis of compounds **3** and KG-TBD for the synthesis of compounds **4**). Two pulsation-free syringe pumps were connected to the reactor allowing a precise control of the flow rate of the toluene solution (0.9 mol/l) of both reagents. The reagents were passed through the reactor in stoichiometric ratio for the synthesis of compounds **3** and in a 3/1 ratio for the synthesis of compounds **4**. Total residence time was 50 and 40 min respectively. The eluates were analyzed by high resolution capillary GC with a fused silica capillary column SPB-20 from Supelco (30 m x 0.25 mm) using decane as internal standard.

References

1. Corma, A. *Chem. Rev.* **1995**, *95*, 559.
<http://dx.doi.org/10.1021/cr00035a006>
2. Clark, J. H.; Macquarrie, D. J. *Chem. Soc. Rev.* **1996**, 303.
<http://dx.doi.org/10.1039/cs9962500303>
3. Sheldon, R. A. *Chem. Ind. (London)* **1997**, 12.
4. Perego, C.; Carati, A. in *Zeolites: From Model Materials to Industrial Catalysts*; Čejka, J.; Pérez-Pariente, J.; Roth, W. J. Eds.; Transworld Research Network: Kerala, 2008; p. 357.
5. Emam, E. A. *ARPN J. Sci. Technol.* **2013**, *3*, 356.
6. Ballini, R.; Bigi, F.; Gogni, E.; Maggi, R.; Sartori, G. *J. Catal.* **2000**, *191*(2), 348.
<http://dx.doi.org/10.1006/jcat.1999.2759>
7. Sartori, G.; Armstrong, A.; Maggi, R.; Mazzacani, A.; Sartorio, R.; Bigi, F.; Dominguez-Fernandez, B. *J. Org. Chem.* **2003**, *68*, 3232.
<http://dx.doi.org/10.1021/jo034044c>
8. Gregori, F.; Nobili, I.; Bigi, F.; Maggi, R.; Predieri, G.; Sartori, G. *J. Mol. Catal. A: Chem.* **2008**, *286*, 124.
<http://dx.doi.org/10.1016/j.molcata.2008.02.004>
9. Maggi, R.; Chitsaz, S.; Loebbecke, S.; Piscopo, C. G.; Sartori, G.; Schwarzer, M. *Green Chem.* **2011**, *13*, 1121.
<http://dx.doi.org/10.1039/c0gc00887g>

10. Jung, M. E. in *Comprehensive Organic Synthesis*; Trost, B. M.; Fleming, I. Eds.; Pergamon: Oxford, 1991, 1.
<http://dx.doi.org/10.1016/B978-0-08-052349-1.00090-1>
11. Bergmann, E. D.; Ginsburg, D.; Pappo, R. *Org. React.* **1953**, *10*, 179.
12. Christoffers, J. *Eur. J. Org. Chem.* **1998**, 1259.
[http://dx.doi.org/10.1002/\(SICI\)1099-0690\(199807\)1998:7<1259::AID-EJOC1259>3.0.CO;2-J](http://dx.doi.org/10.1002/(SICI)1099-0690(199807)1998:7<1259::AID-EJOC1259>3.0.CO;2-J)
13. Soriente, A.; Arienzo, R.; Rosa, M. D.; Palombi, L.; Spinella, A.; Scettri A. *Green Chem.* **1999**, *1*, 157.
<http://dx.doi.org/10.1039/a902102g>
14. Boruah, A.; Baruah, M.; Prajapati, D.; Sandhu, J. S. *Chem. Lett.* **1996**, 965.
15. Ranu, B. C.; Bhar, S. *Tetrahedron Lett.* **1992**, *48*, 1327.
[http://dx.doi.org/10.1016/S0040-4020\(01\)90794-X](http://dx.doi.org/10.1016/S0040-4020(01)90794-X)
16. Rele, D. N.; Trivedi, G. K. *J. Sci. End. Res.* **1993**, *52*, 13.
17. Nelson, J. H.; Howells, P. N.; De Lullo, G. C.; Landen, G. L.; Henry, R. A. *J. Org. Chem.* **1980**, *45*, 1246.
<http://dx.doi.org/10.1021/jo01295a017>
18. Smitha, G.; Patnaik, S.; Reddy, C. S. *Synthesis* **2005**, 711.
19. Ye, W.; Xu, J.; Tan, C.-T.; Tan, C.-H. *Tetrahedron Lett.* **2005**, *46*, 6875.
<http://dx.doi.org/10.1016/j.tetlet.2005.08.010>
20. Ballini, R.; Bosica, G.; Livi, D.; Palmieri, A.; Maggi, R.; Sartori, G. *Tetrahedron Lett.* **2003**, *44*, 2271.
[http://dx.doi.org/10.1016/S0040-4039\(03\)00274-0](http://dx.doi.org/10.1016/S0040-4039(03)00274-0)
21. Xu, J.-M.; Zhang, F.; Wu, Q.; Zhang, Q.-Y.; Lin, X.-F. *J. Mol. Catal. B: Enzym.* **2007**, *49*, 50.
<http://dx.doi.org/10.1016/j.molcatb.2007.08.004>
22. Terent'ev, A. O.; Vil', V. A.; Yaremenko, I. A.; Bitjukov, O. V.; Levitsky, D. O.; Chernyshev, V. V.; Nikishin, G. I.; Fleury, F. *New J. Chem.* **2014**, *38*, 1493.
<http://dx.doi.org/10.1039/c3nj01454a>
23. Cauvel, A.; Renard, G.; Brunel, D. *J. Org. Chem.* **1997**, *62*, 749.
<http://dx.doi.org/10.1021/jo9614001>
24. Subba Rao, Y. V.; De Vos, D. E.; Jacobs, P. A. *Angew. Chem., Int. Ed. Engl.* **1997**, *36*, 2661.
<http://dx.doi.org/10.1021/jo9614001>
25. Mason, B. P.; Price, K. E.; Steinbacher, J. L.; Bogdan, A. R.; McQuade, D. T. *Chem. Rev.* **2007**, *107*, 2300.
<http://dx.doi.org/10.1021/cr050944c>
26. Lempers, H. E. B.; Sheldon, R. A. *J. Catal.* **1998**, *175*, 62.
<http://dx.doi.org/10.1006/jcat.1998.1979>
27. Noda, H.; Motokura, K.; Miyaji, A.; Baba, T. *Adv. Synth. Catal.* **2013**, *355*, 973.
<http://dx.doi.org/10.1002/adsc.201300063>

28. Guideri, L.; De Sarlo, F.; Machetti, F. *Chem. Eur. J.* **2013**, *19*, 665.
<http://dx.doi.org/10.1002/chem.201202698>
29. Campana, A. G.; Fuentes, N.; Gomez-Bengoa, E.; Mateo, C.; Oltra, J. E.; Echavarren, A. M.; Cuerva, J. M. *J. Org. Chem.* **2007**, *72*, 8127.
<http://dx.doi.org/10.1021/jo701354c>
30. Banerjee, S.; Santra, S. *Tetrahedron Lett.* **2009**, *50*, 2037.
<http://dx.doi.org/10.1016/j.tetlet.2009.01.154>
31. Picquet, M.; Bruneau, C.; Dixneuf, P. H. *Tetrahedron* **1999**, *55*, 3937.
[http://dx.doi.org/10.1016/S0040-4020\(99\)00115-5](http://dx.doi.org/10.1016/S0040-4020(99)00115-5)